

Antimicrobial Activity of Silver-Zeolite LTA on Heavily-Contaminated Underground Ghanaian Waters

B. Kwakye-Awuah¹, D. D. Wemegah², I. Nkrumah³, C. Williams⁴, I. Radecka⁵

^{1, 2, 3}Lecturer, Department of Physics, Kwame Nkrumah University of Science and Technology, Kumasi, Ghana

⁴Professor of Mesoporous and Microporous Materials, School of Applied Sciences, University of Wolverhampton, Wolverhampton, WV1 1LY, UK

⁵Principal Lecturer, School of Applied Sciences, University of Wolverhampton, Wolverhampton, WV1 1LY, UK

Abstract: Zeolite LTA was synthesized in the laboratory and loaded with silver ions by isomorphous substitution technique. The silver-loaded zeolite A (Ag-LTA) was characterized by X-ray diffraction (XRD) analysis, scanning electron microscopy (SEM), energy dispersive X-ray (EDX) and Fourier transformed infrared (FTIR) spectroscopy. XRD and SEM analysis showed little or no changes in the phase purity of all zeolites before and after ion exchange or before and after substitution of silver ions. The antimicrobial activity of the silver-loaded zeolite A was investigated by exposing well water samples from Vui community in the Volta Region of Ghana. Parameters such pH, conductivity and temperature as well as microbial analysis were measured before and after addition of silver-zeolite LTA. Profile of the pre-treated water samples showed total and fecal coliforms were between $4.0 \times 10^6 - 1.5 \times 10^7 \frac{\text{MPN}}{100 \text{ ml}}$ and $1.2 \times 10^6 - 1.1 \times 10^7 \frac{\text{MPN}}{100 \text{ ml}}$ respectively whereas *Escherichia coli* were observed to be between $1.2 \times 10^1 - 3.2 \times 10^2 \frac{\text{MPN}}{100 \text{ ml}}$. After exposure to silver-zeolite LTA, all microbial indicator organisms fell below the Minimum Detection Level (MDL) of $20 \frac{\text{MPN}}{100 \text{ ml}}$. Consequently, silver-zeolite LTA could well be a viable antimicrobial agent in the elimination of microbial indicator organisms.

Keywords: Synthesis, zeolite LTA, underground water, silver-zeolite.

1. Introduction

Water, the most abundant raw material on the Earth's surface like any other raw material must be treated before consumption due its universal solvency. Water treatment in general is the various processes carried out on water obtained from natural sources to render it fit for human consumption. According to Tebbutt [26], Montgomery [28] and Rangwala [27], water meant for human consumption must be free from all harmful impurities. Well water including spring waters (ground and surface water) are water that come from deep in the ground through mineral layers [17]. Hence, well waters contain inorganic salts such as calcium and magnesium as well as organic matter. Ground water abstractions in Ghana have been reported to be over 56000 comprising boreholes, hand-dug wells and dugouts [16]. Although perceived to be of more stable and better microbial quality the physical and microbial quality of Ghanaian well water is doubtful [24]. Furthermore, a number of rural folks where water treatment is either absent or very poor have been reported to suffer from water related diseases such as diarrhea, typhoid, cholera and hepatitis A [15, 18]. The cause of such diseases are attributed to anthropogenic activities such as nearness pit latrines, cemeteries, refuse dumps and septic tanks, to wells and boreholes as well as poor hygienic conditions. There has been extensive research into the use of antimicrobial agents. Among the antimicrobial agents silver has been reported to be the most effective agent due to its ability to affect many different functions of microbial cells and non-selective in its antimicrobial action [7] – [10]. Hence, it has antimicrobial activity against a broad spectrum of microorganisms [21, 22].

However, silver ions in any normal containing agent leaches out quickly thereby producing a short resident time.

Zeolites have been found to be an attractive reservoir for silver ions. Zeolites are crystalline hydrated aluminosilicates whose framework structure consists of cavities or pores that are occupied by cations or water molecules. Both the cation and the water molecule have considerable freedom of movements and this permits ion exchange and reversible dehydration [20, 23]. The zeolite structure is made up of a central atom commonly silicon or aluminum surrounded by four oxygen atoms. The tetrahedral atoms, called T-atoms are stacked in beautiful regular three-dimensional arrays such that channels. The zeolite frameworks are typically anionic which are counterbalanced by the positive charges of cations resulting in a high cation exchange capability [19, 21]. Exchangeable cations include lithium, cadmium, lead, zinc, copper, ammonia, silver and protons. The zeolite channels or pores are microscopically small, and have molecular size dimensions in such a way that they are normally termed molecular sieves [23]. In this work, silver ions were incorporated into zeolite type LTA in order to release the silver ions in a controlled and sustained manner. The antimicrobial activity of the silver-zeolite LTA (Ag-LTA) produced was investigated by exposing samples of well and borehole waters from Vui in the Keta District of the Volta Region of Ghana and the extent of removal of total fecal coliforms were determined.


2. Materials and Method

2.1 Water Samples, Zeolite and Media

Water samples were collected from eleven wells in Vui community: eight from the town and three from around the Vui cemetery, two boreholes also in Vui town and one from the tap. The eight samples from the township were labeled K1, K2, K6, K7, K8, K9, K10 and K11. The three samples taken from the cemetery were labeled K3, K4 and K5. In addition, the samples taken from the boreholes were labeled K8B and K9B and the tap water sample was labeled K12. Duplicate samples were collected from the wells and boreholes in sterilized 1.5 L plastic and glass bottles and kept in a container packed with dried ice cubes. The samples were analyzed within 48 hours after collection. Physical parameters such pH and conductivity were measured for each sample. Silver-zeolite LTA was produced in the Water Research laboratory, Department of Civil Engineering, KNUST and characterized in the University of Wolverhampton, UK. One-quarter strength Ringer solutions were prepared by dissolving 1 tablet in 500 ml de-ionized water in a 1 L flask. MacConkey broth was prepared following the manufacturer's protocol. All media were sterilized by autoclaving at 121 °C for 15 minutes.

2.2 Production of silver-zeolite LTA (Ag-LTA)

Zeolite A was synthesized following the method described by Kwakye-Awuah et al [12]. The batch composition for the synthesis is given by:



0.723 g of sodium hydroxide (Aldrich Chemicals, UK) was dissolved in 80 ml of distilled water. The solution was divided into two equal halves and each transferred into plastic beakers. 0.258 g of sodium aluminate (Fischer Scientific Chemicals, UK) was added to the first half with continuous stirring until a homogeneous solution was obtained. 15.48 g of sodium metasilicate (Fischer Scientific Chemicals, UK) was added to other half while mixing until the gel was homogenized. The two samples were mixed quickly and the mixture was again stirred continuously until a homogeneous solution was obtained. 5 ml aliquot of a 0.5 M silver nitrate solution was added to the gel and thoroughly stirred in the dark until a homogeneous phase was obtained. The gel was poured into PTFE-vessels, with each vessel containing about 10 g of the gel. The bottles were put into an electric oven at a temperature of 99 °C for 4 hours. The reaction in the PTFE bottles was quenched by running cold water on the bottles after they were removed from the oven until they were cooled to room temperature. The synthesized samples were filtered using a Buchner vacuum funnel and Whatman No 1 filter paper. The powder samples obtained were washed copiously with 500 ml of distilled water. Following overnight drying of the powdered zeolite at 40 °C in an electrical oven, the zeolite was crushed into uniform powder with pestle and mortar, sieved and stored.

2.3 Characterization of silver-zeolite LTA

As the silver zeolite LTA used for this study was produced in our laboratory, it's essential to characterize it according to its structure, phase purity, chemical composition, molecular vibration states, thermal stability and surface morphology. The phase purity of the Ag-LTA particles was analyzed with X-ray diffraction. The surface morphology and size of the Ag-LTA was examined by scanning electron microscopy (SEM). The chemical composition of Ag-LTA was determined by energy dispersive X-ray analysis (EDX). Thermo Gravimetric Analysis was used to determine the thermal stability of the Ag-LTA and Fourier transform infrared was used to determine the vibrational properties.

2.4 Antimicrobial testing

2.4.1 Escherichia coli (E. coli), total and fecal coliform counts

To enumerate the *E. coli*, total and fecal coliforms 1 ml of each of the samples was serially diluted up to 10^{-3} in a sterile Ringer solution. Starting with sample K1, 1 ml aliquot of each of the dilution were added aseptically to MacConkey broth after which Durham tubes were inverted in the MacConkey broth. Following incubation at 37 °C for 48 hours colour changes in each of the tubes were observed. Tubes with change in colour from pink to yellow indicated the presence of total coliforms and were recorded as positive whereas tubes with no change in colour were recorded as negative. Fecal coliforms were enumerated by preparing a sterilized and unsterilized inoculum cultures. A sterile inoculating loop was inserted into the sterilized bottle containing sterile inoculums and aseptically transferred into another sterilized bottle containing MacConkey broth. The same procedure was repeated for the unsterilized inoculum cultures. The bottles were incubated at 37 °C for 24 hours. After which they were removed, gently shaken to observe the production of gas. The whole procedure was repeated for all the other water samples. Bottles in which there was gas production were recorded as positive and those with no gas production as negative. For the enumeration of *E. coli*, a single total coliform-positive colony was aseptically inoculated into an EC-MUG contained in a sterile test tube. The inoculated tubes were gently shaken to insure adequate mixing after which they were incubated in a water bath at 44 °C for 2 hours. Following incubation, the samples were taken to a dark room to observe whether or not fluorescence with UV light ($\lambda = 366 \text{ nm}$). Samples that gave fluorescence were recorded as positive.

2.4.2 Treatment of water samples with Ag-LTA

The biocidal effect of Ag-LTA as a function of time was investigated by the method given by Kwakye-Awuah et al. [12] with some modifications. A 1000 ml measuring cylinder was used to measure 200 ml of each sample into sterilized conical flasks labeled K1, K2, K3, K4, K5, K6, K7, K8, K9, K10 and K11. Starting with sample K1, 10 mg portion of the Ag-LTA was weighed using an electronic balance and added to the water sample after which the flask was covered with a foam. The procedure was repeated for the rest of the samples. Aliquot portions were withdrawn and analyzed for enumeration of total and fecal coliforms. The flasks containing the Ag-LTA were placed in a rotary shaker and aliquots were withdrawn at 10, 20, 40, and 60 minutes. The

pH and conductivity as well as total and fecal coliforms were enumerated for each sampling time.

3. Results and Discussion

3.1 Characterization of Ag-LTA zeolite

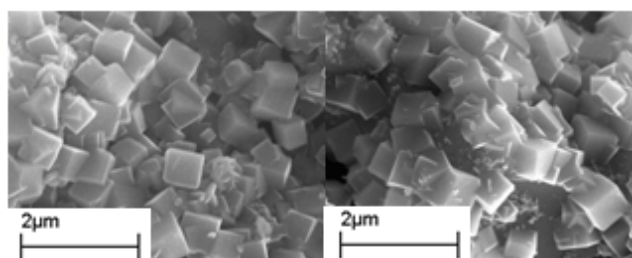


Figure 1: SEM micrograph of zeolite LTA (left) and silver-zeolite LTA (right)

SEM micrograph of the synthesized zeolite LTA and silver-zeolite LTA by isomorphous substitution of silver ions is shown in Figure 1. The crystal morphology showed cubic arrangement in both synthesis routes. Hence, the isomorphous substitution did not alter the crystal properties of the zeolite crystals as confirmed by the XRD spectra (Figure 2). The XRD spectra also showed that the zeolite particles were highly crystalline with no impurity phases present.

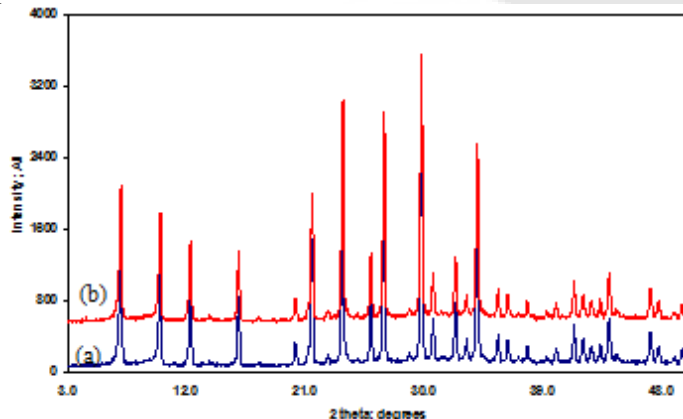


Figure 2: XRD spectrum of (a): zeolite LTA and (b): silver-zeolite LTA.

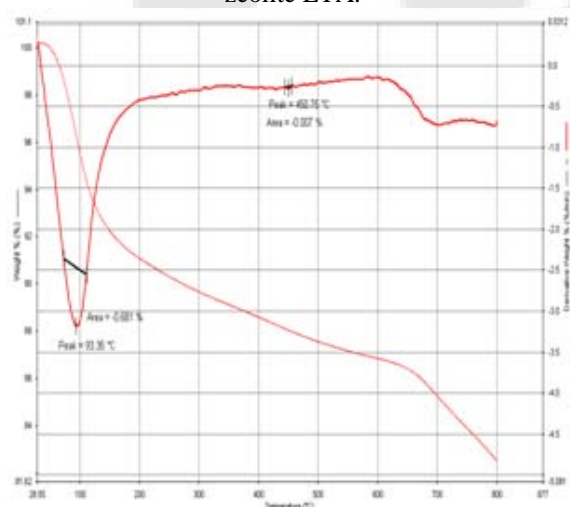


Figure 3: TG-DTA graph of silver-zeolite LTA

Results of the TG-DTA of Ag-LTA is presented in Figure 3. Weight loss of $\approx 1.17\%$ of its total weight occurred between

93.35 showing that Ag-LTA was highly crystalline and that the proportion of absorbed water is very small. A marginal weight loss of $\approx 0.2\%$ of the total weight of Ag-LTA occurred at $450\text{ }^\circ\text{C}$ and can be attributed to loss of chemically bound and adsorbed water within the zeolite framework.

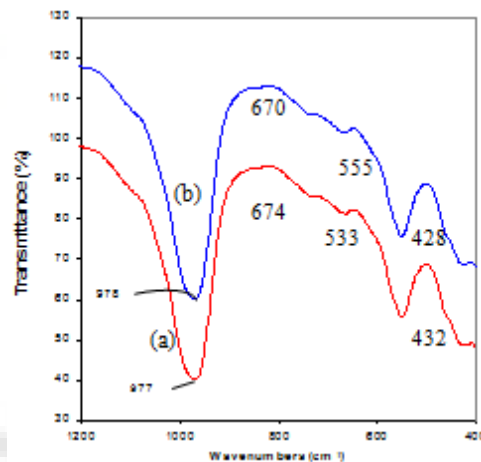


Figure 4: FTIR spectrum of (a): zeolite LTA and (b): silver-zeolite LTA.

The mid-FTIR spectra of the as-synthesized zeolite A (red line) and silver-exchanged zeolite A (blue line) are given in Figure 4 in the region of lattice vibrations ($1200 - 400\text{ cm}^{-1}$). A large broad band was observed in the 977 cm^{-1} in both samples. This band can be attributed to the overlap of the asymmetric vibrations of Si - O (bridging) and Si - O⁻ (non-bridging) bonds. The band shifted towards a slightly higher frequency of 978 cm^{-1} .

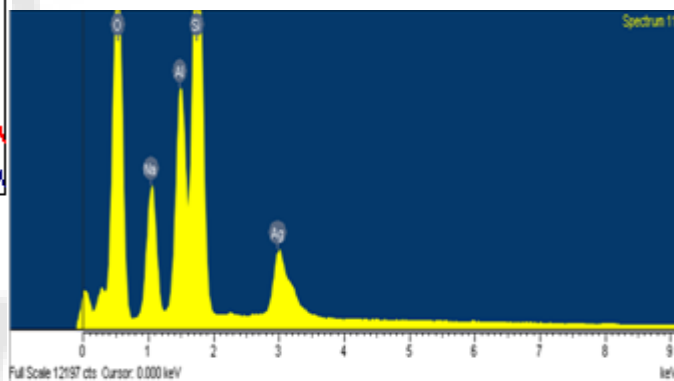


Figure 5: EDX spectrum of silver-zeolite LTA.

EDX spectrum detected silver ions in the zeolite framework after loading (Figure 5). The elemental composition obtained (Table 1) indicates that the atomic concentration of sodium ions decreased by 43.4% after ion exchange. Aluminium ions decreased by 3.9% . The atomic concentration of silver ions on the other hand increased from near zero to 6.8% whilst that of silicon remained fairly constant after ion exchange. Thus the ion exchange of sodium ions by silver ions is likely to have been at the exchangeable sites within zeolite X framework.

Table 2: Physical parameters assessed for the different samples before and after addition of Ag-LTA for duration of 10 minutes

Sample	pH	Conductivity ($\mu\text{S}/\text{cm}$)	Temperature ($^\circ\text{C}$)	Turbidity (NTU)	Total dissolved solids (mg/l)
--------	----	--	----------------------------------	-----------------	-------------------------------

	Before	After	Before	After	Before	After	Before	After	Before	After
K1	7.67	8.35	172	255	25.6	26.6	0.46	0.22	613	1033
K2	7.53	8.19	183	209	25.7	26.7	0.91	0.36	341	1243
K3	7.83	8.13	668	169	25.7	26.8	0.61	0.11	452	1261
K4	7.72	8.03	329	447	25.9	27	0.31	0.17	769	1193
K5	7.38	8.09	207	399	25.9	27.2	0.24	0.16	576	1261
K6	7.41	8.05	455	325	26	27.1	0.68	0.13	488	1012

Table 3: Physical parameters assessed for the different samples before and after addition of Ag-LTA for duration of 20 minutes

Sample	pH		Conductivity ($\mu S/cm$)		Temperature ($^{\circ}C$)		Turbidity (NTU)		Total dissolved solids (mg/l)	
	Before	After	Before	After	Before	After	Before	After	Before	After
K1	7.67	7.84	172	166	25.6	25.5	0.46	0.21	613	1279
K2	7.53	7.75	183	174	25.7	25.5	0.91	0.27	341	1143
K3	7.83	7.71	668	188	25.7	25.8	0.61	0.34	452	1226
K4	7.72	7.56	329	156	25.9	25.8	0.31	0.15	769	1158
K5	7.38	7.6	207	113	25.9	25.8	0.24	0.12	576	889
K6	7.41	7.78	455	145	26	25.9	0.68	0.22	488	1124
K7	7.41	7.75	545	312	26.1	26.1	0.72	0.18	456	936
K8	7.69	7.88	206	189	26.2	26.1	0.52	0.15	422	1001
K9	7.16	7.85	270	201	26.3	26.4	0.92	0.14	455	1066
K10	7.77	7.67	154	133	26.3	26.3	0.34	0.18	436	975
K11	7.39	7.73	336	138	26.6	26.5	0.83	0.12	658	995

Table 1: Elemental composition in the synthesized Ag-LTA

Element	% Atomic weight	
	Before ion exchange	After ion exchange
O	57.4	55.1
Na	5.3	3
Al	15.2	14.7
Si	22.1	22
Ag	0	6.8

3.2 Total coliforms, fecal coliforms and E. coli

Results from the microbial analysis before Ag-LTA addition showed the presence of microbial indicator organisms in the samples obtained from the all the eight wells in the Vui community. In these wells the most probable number of total and fecal coliforms were between 4.0×10^6 - 1.5×10^7 MPN/100 ml and 4.0×10^4 - 1.1×10^7 respectively (Table 5 - 7).The WHO guidelines for drinking water require that the pH and conductivity for drinking water is between 6.5 – 8.5 and 50 – 1500 $\mu S/cm$ respectively.

Table 4: Physical parameters assessed for the different samples before and after addition of Ag-LTA for duration of 30 minutes

Sample	pH		Conductivity ($\mu S/cm$)		Temperature ($^{\circ}C$)		Turbidity (NTU)		Total dissolved solids (mg/l)	
	Before	After	Before	After	Before	After	Before	After	Before	After
K1	7.67	7.34	172	215	25.6	25.6	0.46	0.14	613	1185
K2	7.53	7.25	183	213	25.7	25.6	0.91	0.11	341	1125
K3	7.83	7.34	668	726	25.7	25.7	0.61	0.24	452	1076
K4	7.72	7.31	329	233	25.9	25.7	0.31	0.13	769	99.4
K5	7.38	7.32	207	214	25.9	26	0.24	0.13	57	339
K6	7.41	7.38	455	511	26	26	0.68	0.11	488	976
K7	7.41	7.41	545	556	26.1	26	0.72	0.17	456	1015
K8	7.69	7.38	206	223	26.2	26.2	0.52	0.15	422	1014
K9	7.16	7.44	270	282	26.3	26.2	0.92	0.15	455	98.9
K10	7.77	7.21	154	194	26.3	26.3	0.34	0.13	436	1014
K11	7.39	7.24	336	343	26.6	26.5	0.83	0.15	658	985

Table 5: Microbiological profile of samples taken from various sampling sites in Vui Community after addition of Ag-LTA for 10 minutes.

Sample	E. coli (MPN/10 ml)	Total coliform (MPN/100 ml)	Fecal coliform (MPN/100 ml)
--------	---------------------	-----------------------------	-----------------------------

	Before	After	Before	After	Before	After
Vui Community						
K1	-		1.5×10^7	b.d.l	-	-
K2	3.2×10^2	b.d.l	4.0×10^6	b.d.l	9.3×10^5	b.d.l
K3	1.2×10^1	b.d.l	4.0	b.d.l	4.6×10^6	b.d.l
K4	2.1×10^1		4.0	b.d.l	1.1×10^7	b.d.l
K5	3.2×10^2	b.d.l	4.0	b.d.l	1.5×10^6	b.d.l
K6	1.2×10^1	b.d.l	4.0	b.d.l	1.1×10^7	b.d.l
K7	3.2×10^1	b.d.l	4.0	b.d.l	9.3×10^5	b.d.l
K8	2.1×10^2	b.d.l	-	-	4.3×10^5	b.d.l
Government cemetery						
K9	3.2×10^1		-	-	4.0×10^4	b.d.l
K10	3.2×10^c	b.d.l	-	-	2.1×10^5	b.d.l
K11	-	-	-	-	$1.5 \times 10^{3.2}$	b.d.l
Boreholes						
KB8	-	-	-	-	-	-
KB9	-	-	-	-	-	-

It is also recommended that the temperature of groundwater be between 22 – 29 $^{\circ}C$ Essumang et al [30]. The measured values of the physical parameters of the raw samples (Table 2 – 4) are comparable with the aforementioned WHO guidelines. The pH and conductivity of each sample increased marginally after addition of Ag-LTA. This variation might be as a result of ionic species in the treated water as it was possible to have some Ag^+ ions right after treatment. Nevertheless, the values obtained are well within the WHO guidelines.

Table 6: Microbiological profile of samples taken from various sampling sites in Vui Community after addition of Ag-LTA for 20 minutes.

Sample	E. coli (MPN/10 ml)		Total coliform (MPN/100ml)		Fecal coliform (MPN/100 ml)	
	Before	After	Before	After	Before	After
Vui Community						
K1	-		1.5×10^7	b.d.l	-	-
K2	3.2×10^2	b.d.l	4.0×10^6	b.d.l	9.3×10^5	b.d.l
K3	1.2×10^1	b.d.l	4.0×10^6	b.d.l	4.6×10^6	b.d.l
K4	2.1×10^1		9.0×10^6	b.d.l	1.1×10^7	b.d.l
K5	3.2×10^2	b.d.l	9.0×10^6	b.d.l	1.5×10^6	b.d.l
K6	1.2×10^1	b.d.l	9.0×10^6	b.d.l	1.1×10^7	b.d.l
K7	3.2×10^1	b.d.l	9.0×10^6	b.d.l	9.3×10^5	b.d.l
K8	2.1×10^2	b.d.l	-	-	4.3×10^5	b.d.l
Government						
K9	3.2×10^6		-	-		b.d.l
K10		b.d.l	-	-	2.1×10^5	b.d.l
K11	-	-	-	-	-	b.d.l
Boreholes						
KB8	-	-	-	-	4.0×10^4	-
KB9	-	-	-	-	1.5×10^5	-

Table 7: Microbiological profile of samples taken from various sampling sites in Vui Community after addition of Ag-LTA for 30 minutes.

Sample	E. coli (MPN/10 ml)		Total coliform (MPN/100 ml)		Fecal coliform (MPN/100 ml)	
	Before	After	Before	After	Before	After

Vui Community						
K1	-		1.5X10 ⁷	b.d.l	-	-
K2	3.2X10 ²	b.d.l	4.0X10 ⁶	b.d.l	9.3X10 ³	b.d.l
K3	1.2X10 ¹	b.d.l	4.0X10 ⁶	b.d.l	4.6X10 ⁶	b.d.l
K4	2.1X10 ¹		9.0X10 ⁶	b.d.l	1.1X10 ⁷	b.d.l
K5	3.2X10 ²	b.d.l	9.0X10 ⁶	b.d.l	1.5X10 ⁶	b.d.l
K6	1.2X10 ¹	b.d.l	9.0X10 ⁶	b.d.l	1.1X10 ⁷	b.d.l
K7	3.2X10 ¹	b.d.l	9.0X10 ⁶	b.d.l	9.3X10 ³	b.d.l
K8	2.1X10 ²	b.d.l	-	-	4.3X10 ⁵	b.d.l
Government cemetery						
K9	3.2X10 ¹		8.2X10 ⁵	-	2.1X10 ⁵	b.d.l
K10	3.2X10 ⁶	b.d.l	-	-	2.1X10 ⁵	b.d.l
K11	-	-	-	-	1.5X10 ⁵	b.d.l
Boreholes						
KB8	-	-	-	-	4.0X10 ⁴	-
KB9	-	-	-	-	1.5X10 ⁵	-

E. coli were also enumerated to be between 1.2×10^1 and 3.2×10^1 MPN /100 ml. For samples K9, K10 and K11 obtained from wells from the Keta government cemetery, only K9 contained 8.2×10^5 MPN/100 ml of total coliforms, 2.1×10^5 MPN/100 ml of fecal coliforms and 3.2×10^6 MPN/100 ml *E. coli*. The rest of the samples showed negative results which meant they were somehow devoid of microorganisms. Fecal coliforms of 4.0×10^4 and 1.5×10^5 MPN/100 ml were recorded for samples KB8 and KB9 obtained from boreholes from the Vui community. According to WHO guidelines for potable water there should be complete absence of microbial indicator organisms in any 100 ml of sample of drinking water and not more than 50 total coliforms per 100 ml sample [24, 25, 30 – 32]. It is clear from Tables 4 – 7 that most the wells and boreholes did not meet this required guideline. The existence of total coliforms in water samples has been found to be indication of the presence of pathogenic bacteria such as *Klebsiella*, *Enterobacter*, *Salmonella spp*, *Shigella spp*, *V. cholera*, *Campylobacter*, *Jejuni*, *Campylobacter coli*, and pathogenic *E. coli* [33]. Such microorganisms could cause diseases such as gastroenteritis, dysentery, cholera, typhoid fever among others [3, 4]. Furthermore, Cairncross [1], Kumar, [2] and Jung et al [14] reported that infectious dosage of most of these bacteria could range from $10^5 - 10^8$ whereas others like enteric bacteria (gram-negative) could be as low as 10^1 . The results of this study showed that the use of the wells and boreholes in the Vui community for drinking purposes is likely to cause serious health implications to consumers without prior treatment. Upon the addition of Ag-LTA no indicator microorganisms were observed and enumerated after 10 minutes (Table 5), 20 minutes (Table 6) and after 30 minutes (Table 7). Silver ions have been shown to exhibit both biocidal and bactericidal activity [11, 13, 29]. Although the mechanism of antimicrobial action of silver is not clearly understood to date, its antimicrobial activity is known to affect microorganisms through a number of pathways. The ionic species carries a strong positive charge so it has high affinity for negatively charged groups of biological molecules [5]. These molecules include groups such as sulfhydryl, carboxyl, phosphates and other groups commonly found on macromolecular structures distributed throughout microbial cells [6 – 8]. The binding reaction alters the molecular structure of the macromolecule, rendering it worthless to the cell. The attack effectively inactivates many functions such as cell wall synthesis, membrane transport,

nucleic acids such as RNA and DNA synthesis and translation, and protein folding and function [9, 10]. Because silver affects so many different functions of microbial cells, it is non-selective, resulting in antimicrobial activity against a broad spectrum of microorganisms including bacteria, fungi, and yeasts.

4. Conclusion

The study was conducted to assess the microbial parameter of samples of well and borehole water from Vui community in the Keta District, Volta Region, Ghana and remove the microbial contamination by the action of silver ions incorporated into zeolite LTA framework. Silver-doped zeolite LTA was successfully synthesized in the laboratory as evident in the SEM, XRD, TGA and FTIR results. The synthesized zeolite LTA was applied to heavily-polluted underground waters in Ghana. The microbial parameter of the samples was quantitatively determined and the antimicrobial activity of silver zeolite LTA was shown to be effective, the samples being completely devoid of microorganisms. Since zeolites are inert there as no interaction of the zeolite and microorganisms. The zeolite therefore loosely held the silver ions and released them in a controlled and sustained manner. Future work will explore the longevity and efficiency of antimicrobial action against broad range of microorganisms. Further work will examine the mode of antimicrobial activity on different strains. From the results obtained silver-zeolite LTA has attractive features which make it potentially useful in fabricating operating theater furnitures and fittings.

References

- [1] S. Cairncross, "Water Supply and Sanitation: an agenda for research". The Journal of Tropical Medicine and Hygiene 92(5), pp. 301 – 304, 1987.
- [2] N. Kumar, "A review of freshwater environment". Ecological and Environmental Conservation 3, pp. 3 – 4, 1997.
- [3] R. C. Wright, "The seasonality of bacterial quality of water in a tropical developing country (Sierra Leone)". Hydrobiologia. 96(1), 75 – 82, 1986.
- [4] H. F. Dallas, J. A. Day, "The effect of water quality variables on river and ecosystem". Water Research Commission, Report No. TT61/93, South Africa
- [5] K. M. Poon, "A. Burd, In vitro toxicity of silver: implication for clinical wound care". Burns 30, pp. 140–147, 2004.
- [6] H. Q. Yin, R. Langford, R. E. Burrell, "Comparative evaluation of the antimicrobial activity of Acticoat antimicrobial barrier dressing". Journal of Burn Care Rehabilitation 20, pp. 195–200, 1999.
- [7] W. B. Hugo, "The degradation of preservatives by micro-organisms". International Biodeterioration and Biodegradation. , pp. 185–194, 1991.
- [8] X-C. Li, L. Cai, C. D. Wu, "Antimicrobial compounds from *Ceanothus americanus* against oral pathogens". Phytochemistry 46(1), pp. 97 – 102, 1997b.
- [9] D. Russell, W. B. Hugo, "Antibacterial activity and action of silver". Progress in Medicinal Chemistry. [10]31, pp. 351 – 370, 1994.

- [11] Sondi, B. Salopek-Sondi, "Silver nanoparticles as antimicrobial agent: a case study on *E. coli* as a model for gram-negative bacteria". *Journal of Colloid and Interface Science* 275(1), pp. 177 – 182, 2004.
- [12] B. Kwakye-Awuah, I. Radecka, M. A. Kenward, C. Williams, "Antimicrobial Action and efficiency of silver-loaded zeolite X". *Journal of Applied Microbiology*, 104(5), pp. 1516 – 1524, 2008a.
- [13] B. Kwakye-Awuah, I. Radecka, M. A. Kenward, C. Williams, "Production of silver-doped analcime by isomorphous substitution technique". *Journal of Chemical Technology and Biotechnology* 83(9), pp. 1255 – 1260, 2008b.
- [14] J. Kim, E. Kuk, K. Yu, J. Kim, S. Park, H. Lee, S. Kim, Y. Park, C. Hwang, Y. Kim, Y. Lee, Jeong, M. Cho, "Antimicrobial effects of silver nanoparticles". *Nanomedicine: Nanotechnology, Biology and Medicine*, 3, pp. 95 – 101, 2007.
- [15] W. K. Jung, H. C. Koo, K. W. Kim, S. Shin, S. H. Kim, Y. H. Park, "Antibacterial activity and mechanism of action of the silver ion in *Staphylococcus aureus* and *Escherichia coli*". *Applied and Environmental Microbiology*. 74(7), pp. 2171 – 2178, 2008.
- [16] L. Fewtrell, R. B. Kaufmann, D. Kay, W. Enanoria, L. Haller, J. M Colford Jr, "Water, sanitation and hygiene interventions to reduce diarrhoea in less developed countries: a systematic review and meta-analysis". *Lancet Infectious Diseases*, 5(1), pp. 42 – 52, 2005.
- [17] B. K. Kortatsi, "Ground water utilization in Ghana". In *Proceedings of the Helensinki Conference on Groundwater Resources at Risk*, pp. 149 – 156, 1994.
- [18] C. B. Shirley, G. S. Solt, *An Engineer's Guide to Water Treatment*, Brookfield Gower Publishing, USA, 2002
- [19] M. D. Sobsey, *Managing Water in the Home: Accelerated Health Gains from Improved Water Supply*. WHO Report WHO/SDE/WSH/02.07, WHO, Switzerland, 2002.
- [20] G. Ertl, H. Knözinger, J. Weitkamp, *Preparation of solid catalysts*. Wiley-VCH Verlag GmbH, USA, 1999.
- [21] M. I. Occelli, H. Kessler, *Synthesis of Porous Materials: Zeolites, Clays and Nanostructures*, CRC Press New York, 1997.
- [22] Y. Inoue, M. Hoshino, H. Takahashi, T. Noguchi, T. Murata, Y. Kanzaki, H. Hamashima, M. Sasatsu "Bactericidal activity of Ag-zeolite mediated by reactive oxygen species under aerated conditions". *Journal of Inorganic Biochemistry* 9, pp. 37 – 42, 2000.
- [23] K. Kawahara, K. Tsuruda, M. Morishita, M. Uchida, "Antibacterial effect of silver-zeolite on oral bacteria under anaerobic conditions". *Dental Material* 16, pp. 452 – 455, 2000.
- [24] R. Szostak, *Molecular Sieves*, Science and Technology. Ed. J. J. Weitkamp, Springer, Berlin, 1989.
- [25] K. Obiri-Danso, B. Agyei, K. N. Stanley, K. Jones, "Microbial Quality and Metal Levels in Wells and Boreholes in Some Peri-Urban Communities in Kumasi". *African Journals on Environmental Science and Technology*, 3(1), pp. 59 – 66, 2008.
- [26] M. Rivera-Garza, M. T. Olgun, I. Garcia-Sosa, D. Alcantara, G. Rodriguez-Fuentes, "Silver Supported on Natural Mexican Zeolite as an Antibacterial Material". *Microporous and Mesoporous Materials* 39, pp. 431 – 444, 2000.
- [27] T. H. Y Tebutt, *Principle of Water Quality Control*, Oxford, Pergamon Press Headington Hall, England, 1983.
- [28] S. C. Rwalanga, "Water Supply and Sanitary Engineering", in *Environmental Engineering*, 22nd Ed., Charter Publishing House, India, 1 – 2, 2007.
- [29] M. J. Montgomery, *Water Treatment Principles and Design*. John Wiley and Sons Inc, Canada, 36, 1985.
- [30] M. Catalina, E. M. V. Hoek, "A Review of the Antibacterial Effect of Silver Nanomaterials and Potential Implications for Human Health and the Environment". *Journal of Nanoparticles*, 12, pp. 1531 – 1551, 2010.
- [31] D. K. Essumang, J. Senu, J. R. Fianku, B. K. Nyarko, C. K. Adoko, L. Boampongsem, "Groundwater Quality Assessment: A Physicochemical Properties of Drinking Water in a Rural Setting of Developing Countries". *Canadian Journal of Industrial and Scientific Research*, 2, p.4, 2010.
- [32] WHO, *Guidelines for Drinking Water Quality*. World Health Organization Press, 3(1), 89 – 112, 2004.
- [33] WHO, *Guidelines for Drinking Water Quality*. World Health Organization Press, 3(1), 143 – 168, 2006.
- [34] E. E. Geldreich, *Bacterial Populations and Indicator Concepts in Feces, Sewage, Storm Water and Solid Wastes*, in: *Theory and Practice of Wastewater Treatment*. Ed. R. L. Droste, Wiley, New York, 166, 1997.

Author Profile

Dr. B. Kwakye-Awuah is working as Lecturer in Department of Physics, Kwame Nkrumah University of Science and Technology, Kumasi, Ghana.

D. D. Wemegah is working as Lecturer in Department of Physics, Kwame Nkrumah University of Science and Technology, Kumasi, Ghana.

I. Nkrumah is working as Lecturer, Department of Physics, Kwame Nkrumah University of Science and Technology, Kumasi, Ghana.

Dr. Iza Radecka is working as Principal Lecturer, School of Applied Sciences, University of Wolverhampton, Wolverhampton, WV1 1LY, UK.

C. Williams is working as Professor of Mesoporous and Microporous Materials, School of Applied Sciences, University of Wolverhampton, Wolverhampton, WV1 1LY, UK