

2. Material and Methods

2.1 Materials

All chemicals until specified were purchased from Sigma - Aldrich, Himedia, CDH, QIAGEN and Invitrogen. Glassware's were purchased from Borosil (India). Plasticwares were procured from Tarsons products Pvt. Ltd. (India) and Nunc (Denmark). Breast Tumor Antigen (CA 15-3) from Human Cell Culture was purchased by Sigma -Aldrich. 3' thiol labeled aptamer was purchased by Sigma -Aldrich.

Aptamer sequence- GAAGTGAATATGACAGATCACAACCT [ThiC3]

2.2 Synthesis of GNPs

20nm citrate capped Gold nanoparticles were synthesized. 50 mL of 0.01% HAuCl₄ solution (w/v) was heated to boiling with stirring in a sterile flask. 1000 μ L of 1% (w/v) of trisodium citrate solution was quickly added to the HAuCl₄ solution. After several minutes heating and stirring, the color of the solution was changed from yellow to black and then to red color. Final color of the solution depends on the different sizes of the nanoparticles. The color change is slower for larger nanoparticles compared with small nanoparticles. The amount of citrate solution determines the size of the nanoparticles. Smaller nanoparticles require more citrate solution and whereas larger nanoparticles require less citrate solution. Gold Nanoparticles were characterized by TEM, DLS and UV spectrophotometer.

2.3 Preparation of Apt-GNPs

The Aptamer Goldnanoparticles (Apt-GNPs) conjugate were designed using a modified method (Medley *et al.*, 2008). 5mL of the 20nm gold colloid nanoparticles (GNPs) was centrifuged for 15 min at 13000 rpm. The GNPs were washed three times with 1 mL aliquots of 5mM sodium phosphate buffer (pH 7.6). To wash the GNPs 1mL of 5mM sodium phosphate buffer (pH 7.6) were added in the pellet followed by dispersion through sonication, and centrifuged for 15 min at 13000 rpm in each wash round. After the final wash step, the GNPs were dispersed in 1 mL of the 5mM sodium phosphate buffer (pH 7.6). 50 μ M stock of thiol-labeled DNA sequence (mercaptoethanol treated) was added to wash GNP sample to achieve final concentration 1.5 μ M and incubated for 24 hrs at 4 $^{\circ}$ C. After completion of incubation, the sample was centrifuged at 13000 rpm for 5 min. the sample was washed three times as described previously with the 5mM sodium phosphate buffer (pH 7.6). After, the final wash step, sample was dispersed in 500 μ L of 5mM sodium phosphate buffer (pH 7.6), and stored at 4 $^{\circ}$ C until used. The Apt-GNP conjugate synthesis was characterized through electrophoresis at 2.5% Agarose gel.

2.4 Assay development

The colorimetric assay for the diagnosis of breast tumor antigen was designed according to the following method.

Different concentrations of breast tumor antigen (CA 15-3) i.e. 10, 30, 100, 250, and 500 units were added to 1mL of 1.5 μ M Apt-GNP conjugate in separate tubes and incubated for 30 minutes at 4 $^{\circ}$ C. After completion of incubation 10 μ L of 500mM NaCl were added. Flocculation was detected visually and absorbance was measured using UV-vis spectrophotometer.

3. Results and Discussion

Early and accurate detection of cancer often requires time-consuming techniques and expensive instrumentation. To overcome these limitations, we developed a colorimetric assay for the direct detection of breast cancer. In the present research work we have synthesized 20nm size of Gold nanoparticles. Size of the gold nanoparticles was confirmed by UV-vis extinction spectra and TEM images (figure 1).

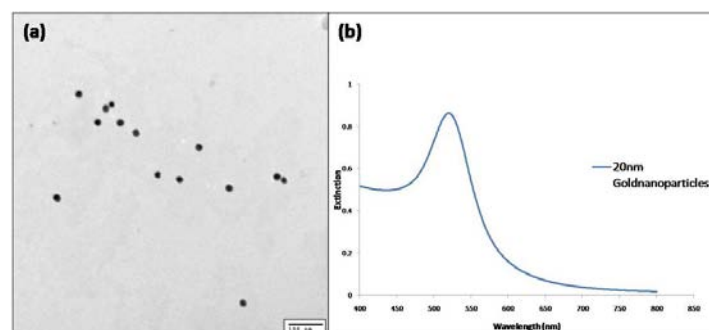


Figure 1: TEM image and UV-vis extinction spectra of 20nm citrate capped Gold nanoparticles.

CA 15-3 specific aptamers were screened from a purchased DNA library through a modified SELEX methodology. Thiolated form of the more stable screened aptamer was synthesized. In the present study we have prepared Apt-GNPs conjugate of 20nm GNPs and different concentrations of screened CA 15-3 specific aptamers. To verify assembling of the aptamer molecules on the surface of the GNPs surface, the washed conjugate sample were checked on 2.5% agarose gel electrophoresis, we found clearly visible bands of DNA in each conjugate. A conjugate having low aptamer concentration shows a blurry or less visible band, while a conjugate with high aptamer concentration shows a sharp band on 2.5% gel (figure 2).

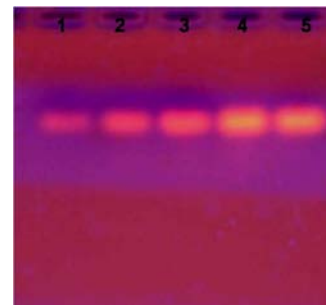


Figure 2: Image showing successful binding of different concentrations (1) 0.15 μ M, (2) 0.75 μ M (3) 1.5 μ M (4) 3.75 μ M and (5) 7.5 μ M of Thiolated aptamer with Gold nanoparticles on 2.5% Agarose Gel Electrophoresis.

To prepare a stable conjugate we have optimized concentration of aptamer and size of Gold nanoparticles. The conjugate of 1.5 μ M aptamer and 20 nm Gold nanoparticle was found more stable. There were no flocculation in the prepared conjugate even we added 10% NaCl. While this Apt-GNPs conjugate solutions was flocculated by adding 500mM NaCl and shows color change, cherry red to purple, in the presence of CA 15-3 (Breast Tumor Antigen). This is might be because of interparticle crosslinking. At low concentration of CA 15-3 no aggregation was observed while at high concentration of CA 15-3 clear aggregation and color change was observed (figure 3). This aggregation was confirmed by TEM images (figure 4).

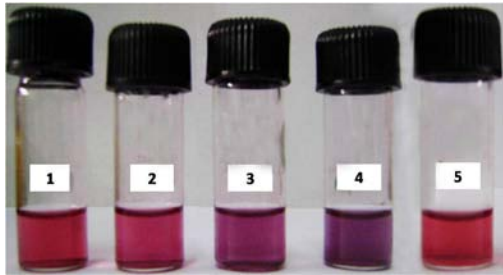


Figure 3: Color change in Apt-GNPs conjugate in presence of (1) 10 units, (2) 30 units, (3) 100 units, (4) 250 units and (5) 500 units of CA 15-3 & 500mM NaCl

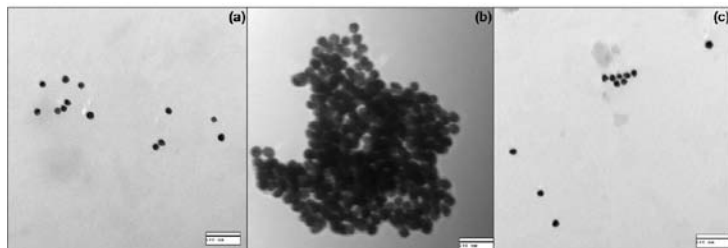


Figure 4: TEM images showing aggregation in the Apt-GNPs conjugate in the presence of (a) 30 units, (b) 250 units and (c) 500 units of CA 15-3.

We believe for the results obtained that, at low concentration of CA 15-3 there were very low interparticle crosslinking, which was not visible, but in case of high concentration of CA 15-3 it was high enough to induce a greater degree of interparticle crosslinking (figure 5) and as a result of aggregation of Apt-GNPs conjugate we observed perfect color change.

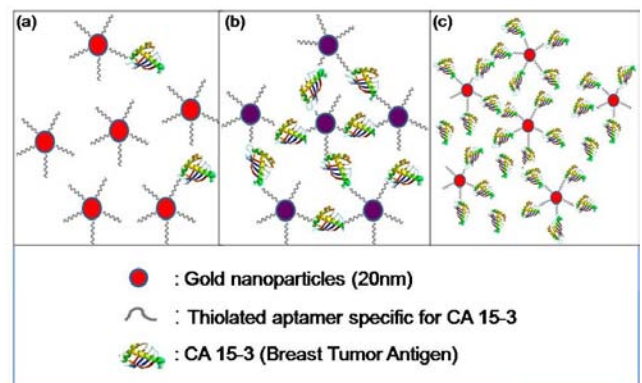


Figure5. Schematic representation of the aggregation of Apt-GNPs conjugates in presence of (a) Low, (b) high and (c) very high concentration of CA 15-3

The reason behind the results obtained was believe that the Apt-GNPs conjugate acts like a bridge in between two Apt-GNPs molecules, which causes the aggregation of conjugate sample. But again at very high concentration of marker we obtained no color change or slight color change i.e. No or very less extent of aggregation, which could be seen only in the data obtained by UV-vis spectrophotometer (figure 6) .

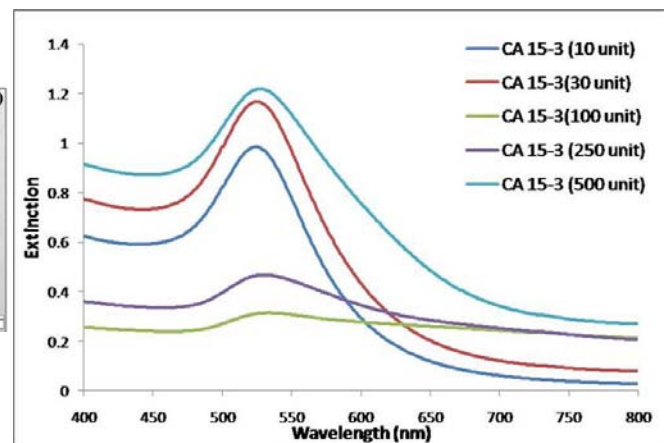


Figure6. UV-vis extinction spectra of Apt-GNPs conjugate in presence of different concentrations of CA 15-3 and 500mM NaCl.

We believe that this is because the aptamer molecules were saturated by the CA 15-3 molecules which causes repulsion in between two Apt-GNPs conjugates. Even it is mentioned in the literature that, the salt induced aggregation of oligonucleotide probe-modified GNPs can readily occur due to the sticky-end pairing effect while addition of target molecules favors the formation of the hairpin structure of probe sequences and substantially inhibits the nanoparticle assembly (Wu *et al.*, 2010). The non specific binding of the Apt-GNPs conjugates were also checked with BSA and no flocculation were found in the presence of BSA (1mg/mL) rather than there were clearly visible flocculation in presence of CA 15-3. Obtained results were also confirmed through UV-Vis spectrophotometer (figure 7).

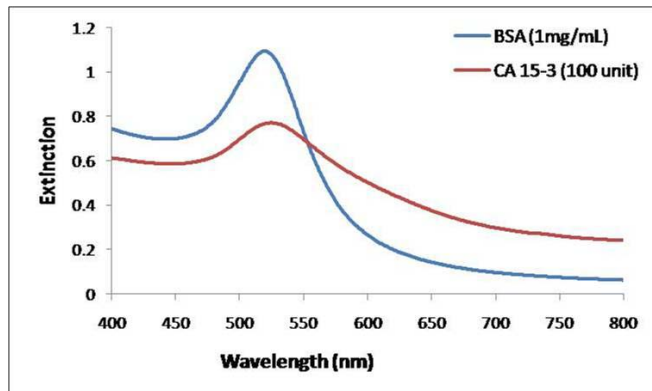


Figure 7: UV-vis extinction spectra of Apt-GNPs conjugate in presence of CA 15-3 & BSA containing 500mM NaCl.

4. Conclusion

The Apt-GNP conjugate have been demonstrated for the very sensitive and specific detection of CA 15-3 (Breast tumor antigen) through utilizing the unique optical properties of Gold nanoparticles and the excellent selective nature of aptamers. We have synthesized 20nm citrate capped Gold nanoparticles and thiol modified aptamer. We have used these 20nm GNPs and thiolated aptamer to synthesize Apt-GNPs conjugates to analyze CA 15-3. The increased concentration of CA 15-3 is easily available in serum if someone is suffering from Breast Cancer. Non specific binding of Apt-GNP conjugate were checked with BSA. In the 5mM sodium phosphate buffer (pH 7.6) and by using 500mM NaCl the Apt-GNPs conjugate act as a probe and specifically and sensitively detected CA 15-3 in patient's serum. The advantages of the present research work was to develop a simple and specific colorimetric assay to diagnose Breast Cancer in early stage, also it was well suited for protein analysis. The future aspects of this work are to develop a diagnostic kit for Breast Cancer by using very simple and specific colorimetric assay and to develop electrochemical biosensor based on Apt-GNPs conjugates.

5. Acknowledgements

The authors would like to acknowledge Dr. H.S. Gour Central University for providing lab facilities. Dr. Yogesh Nangia, institute of microbial technology, Chandigarh is acknowledged for his valuable advices regarding experimental problems. Authors' would like to thank to Dr. Nishima Wangoo and Dr. Rohit K. Sharma, Punjab University, Chandigarh for their kind support to perform all the experiments.

Reference

- [1] Brody, E. N. and Gold, L. 2000. Aptamers as therapeutic and diagnostic agents. *J Biotechnol.* 74:5–13.
- [2] Duffy, M.J. 2001. Biochemical markers in breast cancer: which ones are clinically useful. *Clin Biochem.* 34:347–52.
- [3] Elghanian, R., Storhoff, J. J., Mucic, R. C., Letsinger, R. L., and Mirkin, C. A. 1997. Selective colorimetric detection of polynucleotides based on the distance-dependent optical properties of gold nanoparticles. *Science.* 277:1078–1080.
- [4] Ellington, A. D. and Szostak, J. W. 1990. In vitro selection of RNA molecules that bind specific ligands. *Nature.* 346(6287):818–822.
- [5] Famulok, M., and Mayer, G. 1999. Aptamer as tool in molecular biology and immunology. In: *Combinatorial Chemistry in Biology.* *Curr. Top. Microbiol. Immunol.* 243:123-136.
- [6] Fang, X., Cao, Z., Beck, T., and Tan, W. 2001. Molecular aptamer for real-time oncoprotein platelet-derived growth factor monitoring by fluorescence anisotropy. *Anal. Chem.* 73(23):5752-5757.
- [7] He, H., Xie, C., and Ren, J. 2008. Nonbleaching fluorescence of gold nanoparticles and its applications in cancer cell imaging. *Anal. Chem.* 80:5951–5957.
- [8] Huang, C.C., Huang, Y.F., Cao, Z., Tan, W. H., and Chang, H.T. 2005. Aptamer-modified gold nanoparticles for colorimetric determination of platelet-derived growth factors and their receptors. *Anal. Chem.* 77:5735–5741.
- [9] Lee, J. H., Wang, Z. D., Liu, J. W., and Lu, Y. J. 2008. Highly sensitive and selective colorimetric sensors for uranyl (UO₂²⁺): development and comparison of labeled and label-free DNAzyme-gold nanoparticle systems. *Am. Chem. Soc.* 130:14217–14226.
- [10] Li, H. and Rothberg, L.J. 2004. Colorimetric detection of DNA sequences based on electrostatic interactions with unmodified gold nanoparticles. *Proc. Nat. Acad. Sci.* 101(39):14036–14039.
- [11] Li H., and Rothberg, L. J. 2005. Detection of specific sequences in RNA using differential adsorption of single-stranded oligonucleotides on gold nanoparticles. *Anal. Chem.* 77(19): 6229–6233.
- [12] Li, J., Fang, X., and Tan, W. 2002. Molecular aptamer beacons for real-time protein recognition. *Biochem. Biophys. Res. Commun.* 292(1):31-40.
- [13] Lin, S.Y., Chen, C.H., Lin, M.C., and Hsu, H.F. 2005. A cooperative effect of bifunctionalized nanoparticles on recognition: sensing alkali ions by crown and carboxylate moieties in aqueous media. *Anal. Chem.* 77:4821– 4828.
- [14] Liu, J., and Lu, Y. 2004. Accelerated Color Change of Gold Nanoparticles Assembled by DNAzymes for Simple and Fast Colorimetric Pb²⁺ Detection. *J. Am. Chem. Soc.* 126(39): 12298–12305.
- [15] Liu, J., and Lu, Y. 2006. Fast Colorimetric Sensing of Adenosine and Cocaine Based on a General Sensor Design Involving Aptamers and Nanoparticles. *Angew. Chem., Int. Ed.* 118 (1): 96–100.
- [16] Liu, J., and Lu, Y. 2007. A DNAzyme Catalytic Beacon Sensor for Paramagnetic Cu²⁺ Ions in Aqueous Solution with High Sensitivity and Selectivity. *J. Am. Chem. Soc.* 129(32), 9838–9839.
- [17] Matsui, J., Akamatsu, K., Nishiguchi, S., Miyoshi, D., Nawafune, H., Tamaki, K., and Sugimoto, N. 2004. Composite of Au nanoparticles and molecularly

- imprinted polymer as a sensing material. *Anal. Chem.* 76(5): 1310–1315.
- [18] Medley, C.D., Smith, J.E., Tang, Z., Wu, Y., Bamrungsap, S., and Tan, W. 2008. Gold Nanoparticle-Based Colorimetric Assay for the Direct Detection of Cancerous Cells. *Anal. Chem.* 80: 1067-1072.
- [19] Mirkin, C. A., Letsinger, R. L., Mucic, R. C., and Storhoff, J. J. 1996. A DNA-based method for rationally assembling nanoparticles into macroscopic materials. *Nature.* 382:607–609.
- [20] Nath, N., and Chilkoti, A. A. 2002. A colorimetric gold nanoparticle sensor to interrogate biomolecular interactions in real time on a surface. *Anal. Chem.* 74(3):504–509.
- [21] Stoltenburg, R., Reinemann, C., and Strehlitz, B. 2005. FluMag-SELEX as an advantageous method for DNA aptamer selection. *Anal. Bioanal. Chem.* 383:83–91.
- [22] Storhoff, J. J., Elghanian, R., Mucic, R. C., Mirkin, C. A., and Letsinger, R. L. 1998. One-Pot Colorimetric Differentiation of Polynucleotides with Single Base Imperfections Using Gold Nanoparticle Probes. *J. Am. Chem. Soc.* 120:1959–1964.
- [23] Thanh, N. T. K. and Rosenzweig, Z. 2002. Development of an Aggregation-Based Immunoassay for Anti-Protein A Using Gold Nanoparticles. *Anal. Chem.* 74: 1624–1628.
- [24] Wu Z.S., Lu H., Liu X., Hu R., Zhou H., Shen G., and Yu R.Q. 2010. *Anal. Chem.* 82:3890–3898.
- [25] Zhao, W., Brook M.A. and Li Y. 2008. Design of Gold Nanoparticle-Based Colorimetric Biosensing Assays. *ChemBioChem.* 9(15):2363-2371.
- [26] Zhao, W., Chiuman, W., Lam, J. C. F., McManus, S. A., Chen, W., Cui, Y., Pelton, R., Brook, M. A., and Li, Y. 2008. DNA aptamer folding on gold nanoparticle: From colloid.chemistry to biosensors. *J. Am. Chem. Soc.* 130:3610–3618.
- [27] Zhu, M. Q., Wang, L. Q., Exarhos, G. J., and Li, A. D. Q. 2004. Thermosensitive gold nanoparticles. *J. Am. Chem. Soc.* 126(9):2656–2657.