

# Effect of Stitch Length on Physical and Mechanical Properties of Single Jersey Cotton Knitted Fabric

Elias Khalil<sup>1</sup>, Md. Solaiman<sup>2</sup>

<sup>1</sup>World University of Bangladesh, Department of Textile Engineering, 151/8 Green Road, Dhaka-1205, Bangladesh

**Abstract:** *The physical and mechanical properties of knitted fabric can be changed due to use of various count of yarn, type of yarn (ring, rotor, and compact), quality of yarn, stitch length / loop length, structural geometry, fiber composition of yarn etc. This study focused on the various stitch length effect of grey single jersey. With an increase in stitch length, the dimensional properties like CPI, WPI, GSM, thickness & tightness factor will be decreased for all the structures; while comfort properties like air permeability & water absorbency will be increased. Again shrinkage & spirality will be decreased with increased stitch length at grey stage. Other properties such as bursting strength, abrasion resistance & pilling resistance improved with increased stitch length. Though all the tests for fabric properties were carried out for grey stage, there properties can considerably vary after further finishing of the fabrics. As finishing is mandatory for fabric production, so now-a-days, these kinds of tests are carried out after finishing stage & proper controlling is done according to desired quality. Sometimes, controlling of some properties of finished fabrics are beyond our trial. In that case, analysis of fabric properties at grey stage can help us to take various control & corrective actions when necessary.*

**Keywords:** Stitch Length, Physical Properties, Mechanical Properties, Single Jersey, Knitted Fabric.

## 1. Introduction

Knitting is a method by which thread or yarn is turned into cloth or other fine crafts. Knitted fabric consists of consecutive rows of loops, called stitches. As each row progresses, a new loop is pulled through an existing loop. The active stitches are held on a needle until another loop can be passed through them. This process eventually results in a final product, often a garment. [1]

Knitted loop is a kink of yarn that is intermeshed at its base i.e. when intermeshed two kink of yarn is called a knitted loop. A knitted loop is a basic part of knitted fabric. [2]

Technically a knitted loop consists of a needle loop & a sinker loop. The length of yarn knitted into one stitch in a weft knitted fabric. Stitch length is theoretically a single length of yarn which includes one needle loop & half the length if yarn (half a sinker loop) between that needle loop & the adjacent needle loops on either side of it. Generally larger the stitch length more elastic & lighter the fabric & poorer its cover opacity & bursting strength. Generally stitch length is expressed in mm (millimeter). In the fabrics, loop lengths combine in the form of course lengths & it is there that influences fabric dimensions & other properties like weight, density, shrinkage, spirality etc. Variations in course length between one garment & another can produce horizontal bareness & impair the appearance of the fabric. In the modern knitting machine, it needs to maintain a constant loop length at one feed & another on same machine is mandatory for continuing the constant loop length. Although a machine may be set to knit a specific stitch length, fluctuations in yarn or machine variable can affect yarn surface friction or yarn tension at the knitting point. As a result, the ratio of 'robbed back' to newly-drawn yarn changes & alters the size of the knitted loop. [3]

Effect of stitch length on knit fabric structure plays a vital role on its properties. What kind of properties of single jersey knit structure will be regulated by various stitch length is the measurement of our research.

## 2. Materials and Methods

### 2.1 Materials

100% cotton fiber was taken as raw material to produce 30 Ne carded Z twisted single ring yarn. MV4-3.2 single jersey knitting machine (Mayer & Cie, Germany) was used. Gauge and No. of feeder were 28E and 96 respectively.

### 2.2 Methods

Yarn from the same lot are placed in the creels carefully for knitting. After knitting the samples were dried in relaxed condition & then processed that includes conditioning of the fabrics at 65% relative humidity & 30°C ± 2°C. After relaxation, the following tests were carried out at 27°C ± 2°C & 65% RH.

#### 2.2.1 Stitch Length determination

By the help of HATRA coarse length tester, coarse length of different produced fabrics is measured. Coarse length =  $\pi \times$  diameter of the machine  $\times$  Gauge  $\times$  Stitch length. So, Stitch Length = (coarse length) / ( $\pi \times$  diameter of the machine  $\times$  Gauge). [4]

#### 2.2.2 Determination of WPI, CPI, Stitch density and loop

##### Shape factor

With the help of counting glass we measured WPI & CPI of various stitch length. We calculate stitch density & loop shape factor. [5]

Stitch density = WPI  $\times$  CPI

Loop shape factor = CPI/WPI

### 2.2.3 Determination of Fabric Weight (GSM)

After relaxation & conditioning of knit fabric samples, GSM of samples were tested by taking test samples with the help of GSM cutter & weighting balance (electronic). [6]

### 2.2.4 Determination of Fabric Thickness

After relaxation & conditioning the tubular fabric was turned into open width form by slitting along the slit line measuring tape, the width of the fabric is measured for different stitch length containing samples. [7]

### 2.2.5 Determination of spirality

First cut a sample of (50cm×50cm) with the scissor. Then by the over lock sewing m/c the 4 ends of the cut fabric were sewn. After sewing, again by a scale mark (25cm×35cm) on the fabric & then sample washed with a standard soap solution (1g/l). After washing the sample was tumble dried at 65°C± 15°C for 60 minutes. Then after cooling the sample tested with the shrinkage tester scale also the spirality was tested. Shrinkage was tested length wise & width wise along the mark of (35cm×35cm). And spirality was tested along sewing line alignment. (Distortion of the formation of Loops) [8]

### 2.2.6 Determination of bursting strength

Bursting strength of samples was measured by an automatic bursting strength tester. Samples are gradually set on the diaphragm, the automatic bursting strength tester, measures time, distortion, pressure & the flow rate to burst the fabric. For different samples we recovered there parameters. [9]

### 2.2.7 Determination of Abrasion resistance

The abrasion properly was tested with the help of Martindale abrasion tester. Each specimen of 38mm diameter are cut from the specimen holders with a circle of standard from behind the fabric being tested. The test specimen holders are mounted on the machine with the fabric under test next to the abrading and a pressure of 12 Kpa is applied through a spindle which is inserted through the top plate. After that a revaluation of 10000 cycles is operated & finally the samples are assumed. [10]

### 2.2.8 Determination of pilling resistance

For this test, each specimen is prepared at (125mm×125mm) and cut from the fabric. A seam allowance of 12mm is marked on the back of each square. The samples are then folded face to face & a seam is sewn on the marked line. Each specimen is turned inside out & 6mm cut off each end of it thus removing any sewing distortion. The fabric tabs made are then mounted on rubber tubes. So that the length of table showing at each end is the same. Each of the loose end is taped with PVC tape so that 6mm of the rubber tube is left exposed. All the specimens are then placed in 3 pilling boxes. All the specimens are then placed in 3 pilling boxes. The samples are then tumbled together in a cork – lined box. We used 8000 cycles of revaluations for the test. [11]

### 2.2.8 Determination of Fabric Width

After relaxation & conditioning the tubular fabric was turned

into open width form by slitting along the slit line measuring tape, the width of the fabric is measured for different stitch length containing samples. [12]

## 3. Result and discussion

### 3.1 Effect on WPI, CPI, Stitch density and loop shape factor


When stitch length increased, the WPI, CPI, stitch density, loop shape factor, decreased correspondingly. Table 1 for different stitch length in single jersey fabric represents the change of WPI, CPI, stitch density & loop shape.

**Table 1:** Change of WPI, CPI, Stitch density and loop shape factor with different stitch length

Obs. no	Stitch length(mm)	WPI	CPI	Stitch density (WPI × CPI)	Loop shape factor
01	2.50	30	62	1860	2.67
02	2.60	29	59	1711	2.03
03	2.70	28	57	1596	2.04
04	2.74	28	56	1568	2.00
05	2.78	27	54	1458	2.00
06	2.85	25	51	1275	2.04
07	3.05	21	46	966	2.19

### 3.2 Effect on Fabric Weight (GSM)

GSM depends on knit structure, yarn count & dimensional properties of knit fabrics. When fabrics density is more, fabrics weight is also more. From the figure 1 it is found that, fabric GSM decreases with the increased stitch. GSM can also vary for some yarn characteristics used in the formation of fabric.

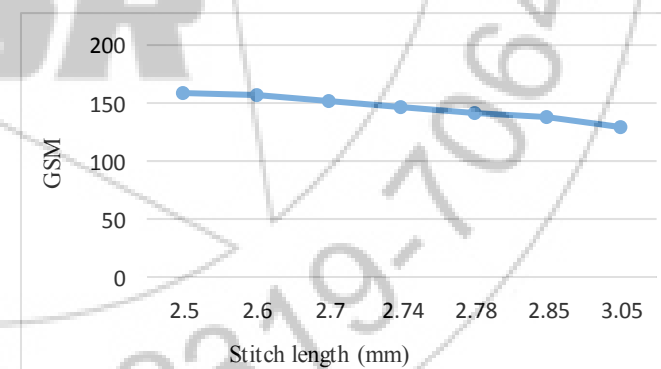

**Figure 1:** Change of GSM of fabric with stitch length

### 3.3 Effect on Fabric Thickness

Fabric thickness depends on loop shape, compactness of structure & relative closeness of the loops.

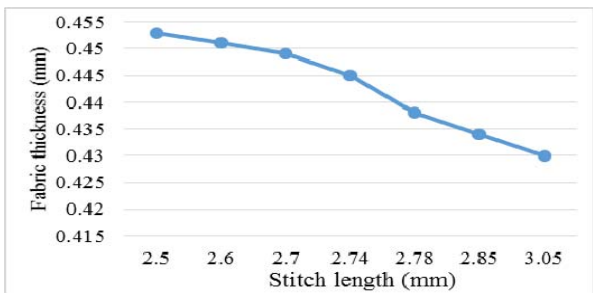


Figure 2: Change of Fabric Thickness with stitch length

From the figure 2 it is found that, fabric thickness decreases with the increased stitch length. Thickness can also vary for high yarn diameter, low yarn twist, less lateral compression force etc.

3.4 Effect on Fabric Width (Open Width)

Fabric width depends upon the bending property of loops, type of loops employed, yarn count, cylinder diameter etc.

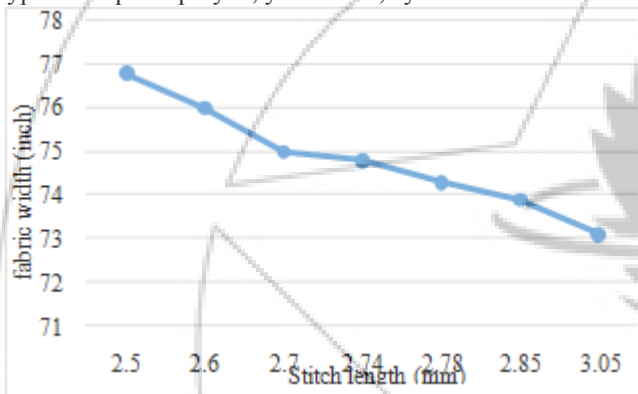


Figure 3: Change of width with stitch length

From the figure 3 can see that with the increasing value of stitch length, fabric width is decreased. This is due to when stitch length increases the loop is less bent than the tension impose upon it. As a result after relaxation, the loops go to their flexible bent position without altering stitch length.

3.5 Change in Bursting Strength

From the figure 4 we can see that if the stitch length increases, bursting strength is decreased. This is due to the fact that, when stitch length is less, no. of loops per square inch is more. Therefore, the resistance towards the force is more in case of less stitch length of fabric

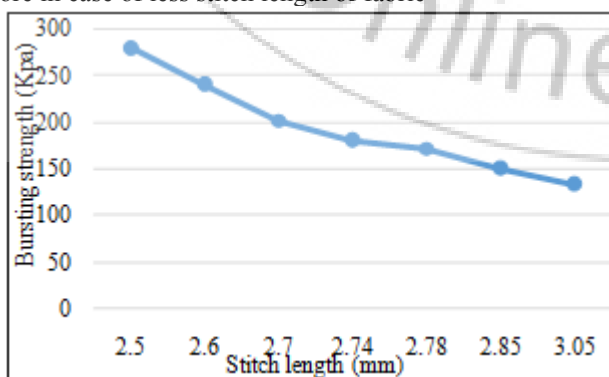


Figure 4: Effect of stitch length on bursting strength

3.6 Change in Abrasion Resistance

The abrasive wear of a material depends on the construction of the yarn & the structure of the fabric. It was established that abrasion was less for higher density fabrics. This was because of the fact, when the density was more, more loops contributed to the wear & so its abrasion resistance increased.

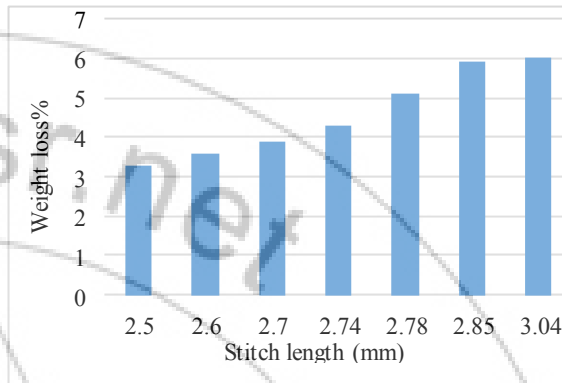


Figure 5: Effect of stitch length on abrasion resistance

From figure 5 it is seen that, Single jersey fabric showed higher abrasion loss% due to its soft nature on the surface.

3.7 Effect on Pilling Resistance

Table 2: Change of Pilling Resistance of fabric with stitch length

Obs. no.	Stitch Length(mm)	Pilling Resistance (rating)
1	2.50	1-2
2	2.60	1-2
3	2.70	1-2
4	2.74	1
5	2.78	1
6	2.85	1
7	3.05	1

From table 2, it is seen that, as the stitch length increased, the pilling grade values decreased from higher to lower grade. Again, it has been seen that, pilling resistance is very low.

3.8 Effect on Shrinkage

Shrinkage is an inherent property of knit fabrics which can't be prohibited, but for better quality, it must be controlled in a systematic way. After tumble drying & cooling of the fabric, shrinkage of this samples are measured both lengthwise & widthwise.



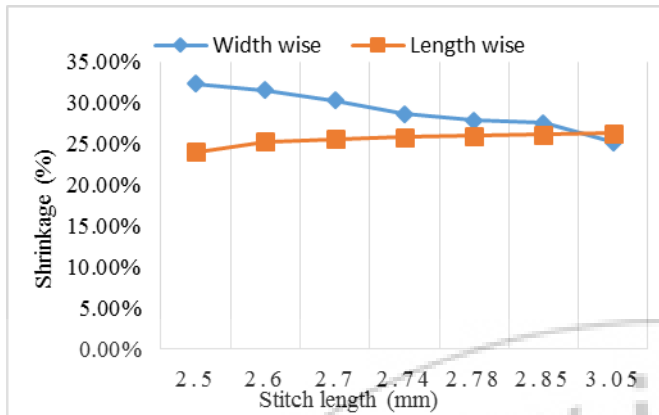


Figure 6: Effect of stitch length on Shrinkage

From figure 6 we can see that with the increase of stitch length, widthwise shrinkage is decreasing while lengthwise shrinkage is increasing. As the results are found in grey stage. So results are not compatible with the finished fabric. Because, after treatment shrinkage properties can remarkably be changed.

### 3.9 Change in Spirality

Spirality is the distortion of the place of loops where they formed. This is tested along with shrinkage test. It is also an inherent dimensional properties of knit fabrics, which is mostly found in single jersey fabrics. From figure 7 it is obvious that with the increase in stitch length, spirality is decreasing.

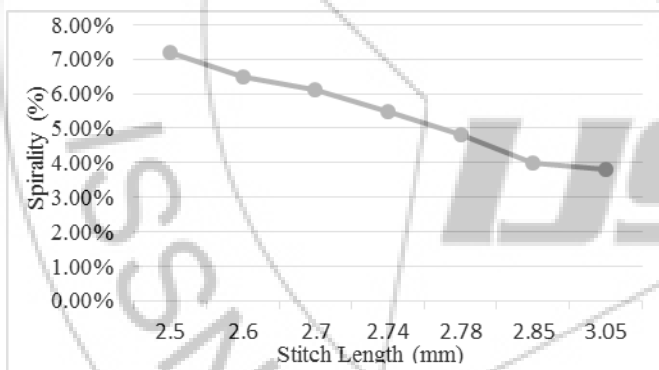


Figure 7: Effect of stitch length on spirality

## 4. Conclusion

Stitch/Loop length is the fundamental unit which controls all the properties of weft knitted fabrics. Mainly stitch length & knit structure affects all the dimensional, comfort, handle & other properties. We only worked on single jersey, but stitch length also plays a great roll on other structures also. From the analysis, we can get idea about grey stage of knit fabrics, that source will show better performance for the summer inner wear & some for winter outwear. It can be decided that very low stitch length is not also good. For a uniform comfort, handle & tensile properties in the fabric moderate stitch length should be maintained, which in the long run also depends upon the quality, cost & profit of the industry.

## References

- [1] <https://en.wikipedia.org/wiki/Knitting> Retrieved on 20 July 2014
- [2] S.A Belal, Understanding Textiles for a Merchandiser, BMN foundation Press, Dhaka, 2009.
- [3] N. Anbumani, Knitting Fundamentals, Machines, Structures and Developments, New Age International, India, 2007.
- [4] Munden, D. L. Hatra research, report no. 9, April-1959.
- [5] IS 1963: 1982, Methods for determination of threads per unit length in knitted fabrics, Bureau Of Indian Standards, New Delhi – 110002
- [6] ASTM D3776 / (2013), Standard Test Methods for Mass per Unit Area (Weight) of Fabric, American Society for Testing and Materials, West Conshohocken, PA, USA.
- [7] ASTM D1777 - 96(2011), Standard Test Method for Thickness of Textile Materials
- [8] AATCC Test Method 187-2013, Dimensional Changes of Fabrics: Accelerated, American Association of Textile Chemists and Colorists, Research Triangle Park, N.C., USA, Developed in 2000.
- [9] ASTM D3786 / 2013, Standard Test Method for Bursting Strength of Textile Fabrics, Diaphragm Bursting Strength Tester Method.
- [10] ISO 12947-1:1998 □2010, Textiles -- Determination of the abrasion resistance of fabrics by the Martindale method -- Part 1: Martindale abrasion testing apparatus, Geneva, Switzerland
- [11] ASTM D4970 / (2010), Standard Test Method for Pilling Resistance and Other Related Surface Changes of Textile Fabrics; Martindale Tester.
- [12] ASTM D3774 - 96(2012), Standard Test Method for Width of Textile Fabric.

## Author Profile



**Elias Khalil** received the B.S. degree in Textile Engineering from Bangladesh University of Textiles (BUTex) in 2011. During 2011-2013, he stayed in National Institute of Engineering and Technology (NIET) and Textile Industry. His concentration areas are Apparel Manufacturing, Etextiles, Geotextiles, Wet Processing, and Nanotechnology in textiles, Polymer, Application of Computer in Textiles. His M.Sc. in Textile Engineering is ongoing at BUTex and now working as a Co-coordinator & Lecturer in Department of Textile Engineering at World University of Bangladesh.



**Md. Solaiman** received the B.S. degree in Textile Engineering from Bangladesh University of Textiles (BUTex) in 2007 and M.S from Mawlana Bhashani Science and Technology University. During 2007-2010, he stayed in Texeurope (BD) limited as a Production officer, Technical service executive at American & Efrid Bangladesh Limited. His concentration areas are weaving, knitting, Technical textiles, and Nanotechnology in textiles. Presently he is working as a Head (acting) of Department of Textile Engineering at World University of Bangladesh.