

# Strength Properties of Concrete by the Influence of Flyash and Nanosilica as a Partial Replacement of Cement

G. Yamini<sup>1</sup>, Dr. S.Siddiraju<sup>2</sup>

<sup>1</sup>PG Student, Department of Civil Engineering, Siddarth Institute of Engineering & Technology, Puttur, Andhra Pradesh, India

<sup>2</sup> Professor & Head, Department of Civil Engineering, Siddarth Institute of Engineering & Technology, Puttur, Andhra Pradesh, India.

**Abstract:** *With the aim of lessening the carbon dioxide emissions because of the manufacture of cement there is an emergence to find an opportunity answer for this problem. As a solution we will add fly ash and nano silica to regular Portland cement which reduces the environmental effect, but additionally improves the electricity traits of concrete. Latest developments in nano-era and availability of nano-silica (nS) have made using such materials in improving concrete residences possible. it is possible because the silica (S) in the sand reacts with calcium hydrate (CH) within the cement at Nano scale to shape. C-S-H gel and thereby it improves the strengthening element of concrete, which might be in turn useful within the accomplishing high Compressive power even in early days. This experimental thesis consists of state of the artwork of nS application in concrete, importance of nS, the nS manufacturing manner, the determination of compressive energy, split tensile strength, flexural strength at and comparing the consequences to controlled concrete of M30 grade. In this experimental approach the cement is partly replaced via 20% and 30% of Fly Ash and Nano-Silica through 1.5%, 3.0% and 4.5% by using weight. The nature of mixed Fly Ash and Nano-Silica on compressive strength, Split tensile power, flexural energy of M30 grade of concrete is investigated. The version of various test results of concrete organized with diverse proportions of Fly Ash and Nano-Silica shows the equal trend. Based totally at the take a look at effects, it may be located that concrete organized with 20% Fly Ash and 3.0% Nano-Silica addition possesses enhanced characteristics compared to the control concrete. The boom in energy traits of concrete prepared using Fly Ash and Nano-Silica can be attributed to the effective particle packing.*

**Keywords:** Fly-Ash, Nano-Silica, Partial substitute, Particle Packing and Calcium silicate Hydrate.

## 1. Introduction

The speedy improvement of buildings and civil engineering after the second global warfare is characterized by using huge application of Concrete because the first-rate construction material. Inside the growing creation discipline concrete plays a major role. New sorts of systems and new technology in constructing, structural and civil engineering Created greater tough requirements for this material. Cement intake will become an increasing number of very hastily all over the globe. There's a need to reduce the co2 emissions inside the environment. One of the treatments to overcome this example is to reduce the cement content material and make use of Pozzolanic materials for the training of concrete. Some of them are Metakaoline, GGBS, Fly Ash, and Micro Silica and so on. After a long time a constituent in concrete is partially replaced by means of a nano fabric (Nano-Silica). The ASTM defines Pozzolanas "as chemically reacting materials with calcium hydroxide at regular temperatures to make compounds consisting cementitious features".

One of the great acknowledged Pozzolanic materials inside the world is FLY ASH. Nano-silica particulates are too small which tends to mingle and mix uniformly with all the materials in a perfect manner which results in proper bonding. Fly ash while reacted in the presence of water produces better order hydrated products enhances power and improves sturdiness(durability). The mechanism of mixed application of fly ash and nano-silica is to be determined out.

## 2. Objective

The objectives of the prevailing research work are to examine the impact of Fly ash content material on compressive strength, split tensile strength and flexural strength of concrete, combined effect of application of Nano-Silica and Fly ash on compressive strength, split tensile energy and flexural strength and assessment of the consequences of traditional Concrete, with the influence of Fly ash and Nano-Silica as substitute of Cement

## 3. Experimental Programme

150 mm × one hundred fifty mm × 150 mm cubes, cylinders of a hundred and fifty mm diameter × 300 mm peak and prisms of 100 mm × 100 mm × 500 mm were casted in this thesis. At extraordinary curing durations (3, 7, 28 and fifty six days) Concrete cubes had been examined for energy evaluation. At the age of 28 days cylindrical specimens had been examined for finding out the power of the concrete via distinctive tests like split tensile strength check, and compressive strength check. For determining the flexural electricity of concrete prisms has been used.


## 4. Effects and Considerations

### 4.1 Compressive Strength


For a spread of proportions of fly ash and nano-silica the version of the cube compressive electricity of M30 grade concrete with age is proven in Fig.1. The average of 3 take a look at consequences offers the cube compressive electricity.

It may be witnessed that the electricity of concrete using fly ash and Nanosilica prospers greater electricity than the manipulate concrete until three% of nano-silica and 20% of

fly ash. If the improve in nano-silica and fly ash if extended more then the power of the concrete declines.

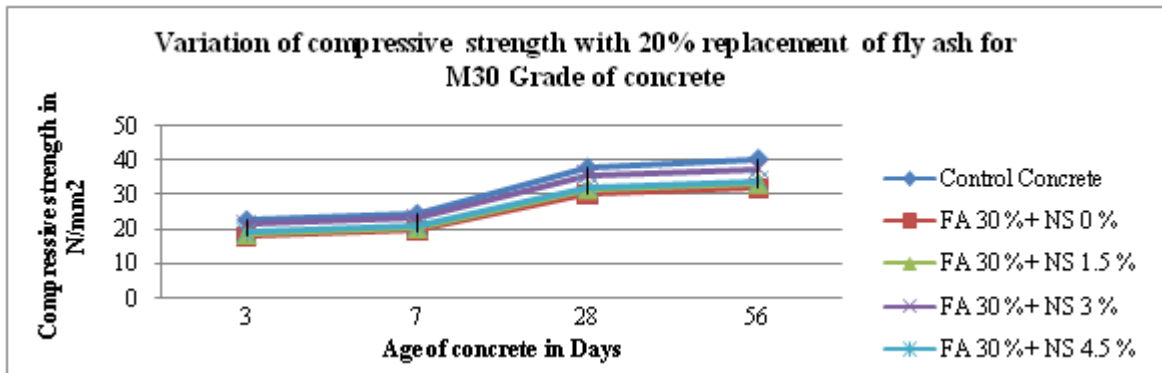

1. 20% Fly Ash

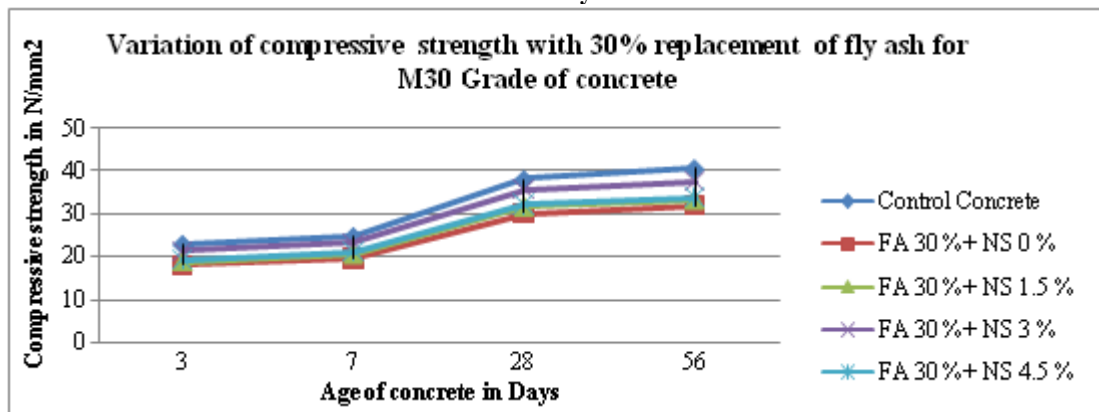

2. 30% Fly Ash

Figure 1: Version of Cube Compressive Electricity of M30 Grade Concrete with Age for Distinct Percentages of Fly Ash and Nano-Silica

#### 4.2 Split Tensile Strength

The dissimilarity of split tensile energy of M30 grade of concrete with Nano-Silica for diverse possibilities of fly ash is proven in Fig. 2. Control concrete's split tensile strength is 4.37 N/mm<sup>2</sup>. The split tensile power of concrete to start with improved till 3% of Nano silica for whatever percent of fly

ash and moreover the strength lessens with addition in the Nano-silica. It could additionally be found that at a mixture of 3% of Nano silica and 20% fly ash maximum break up tensile power may be received. The increase in split tensile energy of concrete with 3% Nano-Silica and 20% fly ash content material is 3%.

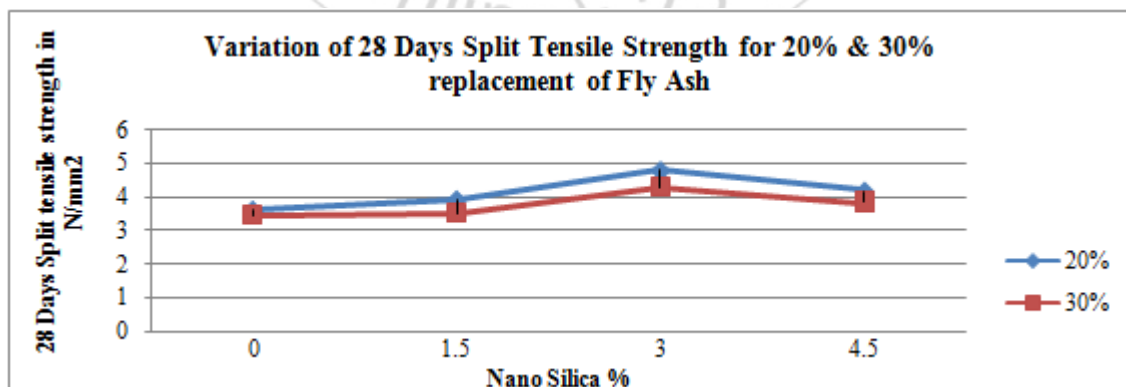



Figure 2: variant of Split Tensile Energy of M30 Grade of Concrete with different possibilities of Nano-Silica and Fly Ash

#### 4.3 Flexural Strength

The alteration of flexural power of M30grade of concrete including diverse magnitudes of fly ash and nano-silica is seen in Fig.3. Normal concrete has its flexural energy as 5.89 N/mm<sup>2</sup>. Initial boom of flexural strength of concrete

takes place until three% of Nano-Silica for wonderful percent of fly ash after which with similarly growth in the Nano-Silica the magnitude of flexure decreases. The endorsed mixture for maximum split tensile power is 3% of Nano-silica and 20% of fly ash. The growth in the flexural

strength concrete with 3% nano-silica and 20% fly ash content is 3.4%.

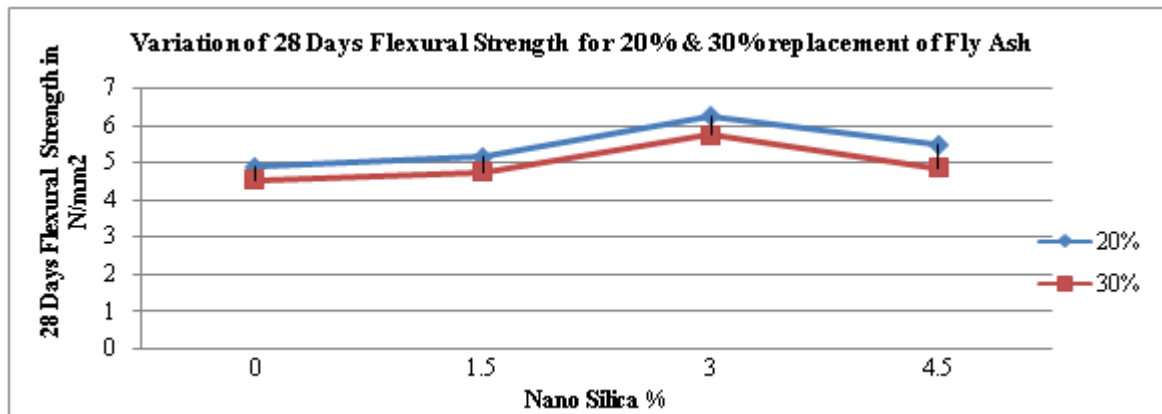

**Figure 3:** Variation of Flexural Strength of M30 Grade of Concrete with Distinct Percentages of Nano-Silica and Fly Ash

## 5. Conclusions

On the basis of the studies completed, it may be concluded that in the binary device, silica will increase the tremendous plasticizer demand at a constant workability because of its excessive surface area. Fly ash addition, alternatively, decreases the water demand. Nano concrete should control the carbon dioxide emission from the earth which is proven with the aid of the usage of fly ash concrete products in place of cement concrete. for this reason the Nano particles that's in the form of silica can easily react with cement particles which might be commonly in Nano scale initiate the CSH response and consequently its tend to boost up the compressive energy of concrete. Nano-silica consumes calcium hydroxide crystals, reduces the size of the crystals at the interface area and transmutes the calcium hydroxide feeble crystals to the C-S-H crystals, and improves the interface sector and Cement paste structures. The consequences of the experimental investigation imply that the fly ash and nano-silica may be followed as ordinary Portland cement substitute for concrete guidance. the usage of the test effects, it may be concluded that with the increase in the percentage of nano-silica the various electricity traits of concrete extended up to 3%, with further growth in the nano-silica the power characteristics of concrete are decreased for the given probabilities of fly ash. it's miles very interesting to be aware that the variation of compressive energy, split tensile power, and flexural strength of M30 grade fly ash concrete with nano-silica suggests the similar trend. The numerous power characteristics of concrete can be improved through the addition of 3% nano-silica and 20% fly ash content. it is able to be concluded that the cement content can be reduced without compromising the power of concrete with the aid of the use of fly ash and nano-silica aggregate at the right share.

## References

[1] Dr. D. V. Prasada Rao and K. Jayalakshmi, "Experimental Investigation on the Properties of Nano-Silica Concrete", International Journal of Civil Engineering & Technology (IJCIET), Volume 5, Issue 6,

2014, pp. 116 - 124, ISSN Print: 0976 - 6308, ISSN Online: 0976 - 6316.  
 [2] IS: 10262-2009. Concrete Mix Proportioning - Guidelines (First Revision). Bureau of Indian Standards, New Delhi.  
 [3] Dr. D. V. Prasada Rao and G. V. Sai Sireesha, "A Study on the Effect of Addition of Silica Fume on Strength Properties of Partially used Recycled Coarse Aggregate Concrete", International Journal of Civil Engineering & Technology (IJCIET), Volume 4, Issue 6, 2013, pp. 193 - 201, ISSN Print: 0976 - 6308, ISSN Online: 0976 - 6316.  
 [4] Dr. D. V. Prasada Rao and M.Pavan Kumar, "A Study On Influence Of Fly Ash And Nano- Silica On Strength Properties Of Concrete", International Journal Of Advanced Research In Engineering And Technology (IJARET), Volume 5, Issue 7, July (2014), pp. 94-102, ISSN 0976 - 6480 (Print) ISSN 0976 - 6499 (Online)  
 [5] P.A. Ganeshwaran, Suji and S. Deepashri, "Evaluation of Mechanical Properties of Self Compacting Concrete with Manufactured Sand and Fly Ash" International Journal of Civil Engineering & Technology (IJCIET), Volume 3, Issue 2, 2012, pp. 60 - 69, ISSN Print: 0976 - 6308, ISSN Online: 0976 - 6316.  
 [6] Chandra S, Bjornstrom J, „Influence of cement and superplasticizers type and dosage on the fluidity of cement mortars - Part I, cement and Concrete Research, 32, (2002), 1605 - 1611.  
 [7] Balaguru, P. N. (2005), "Nanotechnology and Concrete: Background, Opportunities and Challenges." Proceedings of the International Conference - Application of Technology in Concrete Design  
 [8] Dr.S.Siddiraju and S. Reshma, " An Experimental Investigation on Concrete with Nano Silica and Partial Replacement of Cement with Flyash", International Journal of Science and Research, Volume 4 Issue 7, July 2015 , (IJSR) ISSN (Online): 2319-7064  
 [9] www.aggregateresearch.com  
 [10] www.Nanoc.info/index.html  
 [11] www.nanoforum.org