

Acoustical Investigations in NiFe₂O₄ Nanofluid

Navneet Yadav¹, Aashit Kumar Jaiswal², Satyendra Singh³, D.K. Singh⁴, R.R. Yadav

Department of Physics, University of Allahabad, Allahabad-211002, India

Abstract: Synthesis of nanosized ferrite particles has become an important part of modern research. In the present investigation, we have synthesized NiO, Fe₂O₃ and NiFe₂O₄ nanofluids using sol-gel method. The particle size distribution of the prepared nanoparticles has been determined using acoustic particle sizer (APS-100). It is based on measurement of ultrasonic attenuation and velocity depending upon the frequency. Ultrasonic velocity measurements in synthesized nanofluids have been made using the ultrasonic interferometer at different thermal conditions.

Keywords: Nickel ferrite, Sol-Gel synthesis, Acoustic Particle Sizer (APS).

1. Introduction

Synthesis of nanosized ferrite particles is a subject of intensive research and has become an important part of modern research. Magnetic properties of nanosized ferrite particles have attracted considerable attention because of their unique properties [1-3]. In recent years, a number of researchers have prepared nanosized ferrites by emulsion method, co-precipitation method, hydrothermal method, reverse micelle technique, high energy ball milling technique and pulsed wire discharge method [3-6]. Nickel ferrite (NiFe₂O₄) is technologically important magnetic material extensively used in high frequency applications such as microwave device due to its high resistivity and sufficiently low losses [7].

Here, in the present investigation, we have synthesized NiO, Fe₂O₃ and NiFe₂O₄ nanofluids using sol-gel method. The particle size distribution of the prepared nanofluids has been determined using acoustic particle sizer (APS-100). It is based on measurement of ultrasonic attenuation and velocity depending upon the frequency [8]. Further, ultrasonic velocity measurements in NiO, Fe₂O₃ and NiFe₂O₄ nanofluids have been made using the ultrasonic interferometer at different thermal conditions.

2. Experiment Section

Nanofluids of NiO, Fe₂O₃ and NiFe₂O₄ have been prepared by using well-known sol-gel method. The precursors [Nickel acetate tetra hydrate {(CH₃COO)₂Ni.4H₂O} and Iron (III) nitrate nonahydrate {Fe(NO₃).9H₂O}] used in the synthesis were AR grade. The particle size distribution measurements have been done by an acoustic particle sizer (model APS-100, Matec Applied Sciences, Massachusetts, USA). Ultrasonic velocity in the nanofluids has been measured with the help of a variable path interferometer technique at 4 MHz in the temperature range 30-80 °C.



Figure 1: Photograph of Acoustic Particle Sizer (APS-100)

3. Results and Discussion

The photograph of APS-100 used in our study has been shown in Fig. 1. This technique consists of propagating ultrasonic waves of a range of frequencies (1 to 100 MHz) through the system and measuring the attenuation (dB/cm) at each frequency. The attenuation level, as well as, the shape of the acoustic attenuation curve is related to the particle size distribution (PSD). This attenuation spectrum can be converted to a particle size distribution

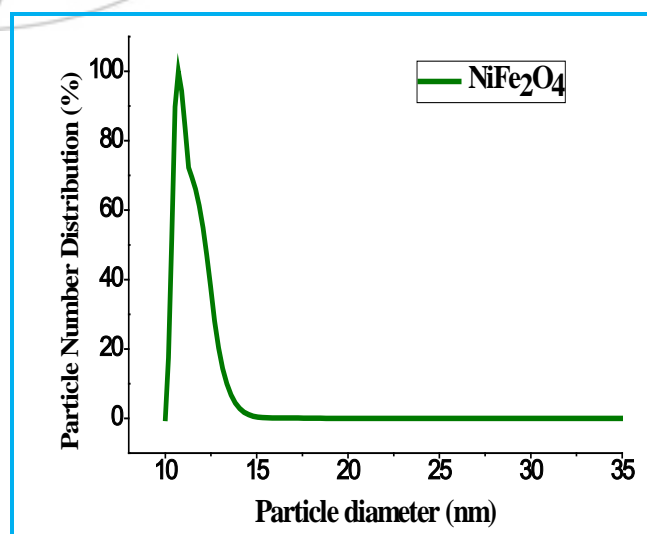


Figure 2: Particle size distribution curves of nanofluids

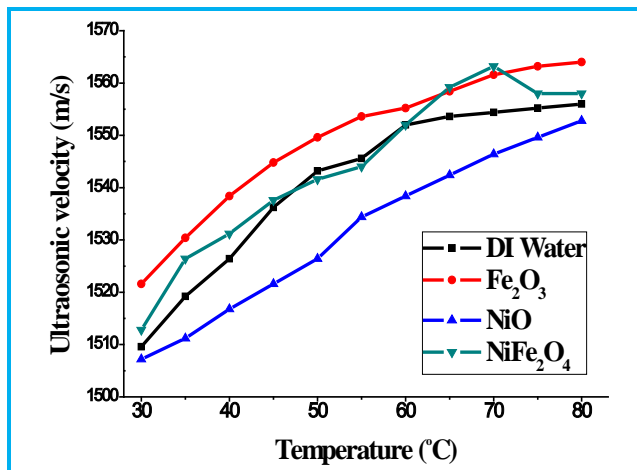


Figure 3: Temperature dependent ultrasonic velocity in nanofluids at 4 MHz.

[8]. The measured particle size distribution in the prepared NiFe₂O₄ nanofluid with the help of acoustic particle sizer is shown in Fig. 2, which clearly indicates the size of the NiFe₂O₄ nanoparticles found to be in the range 10 – 15 nm, while the maximum number of particles is of size 11 nm.

The ultrasonic velocities measured for pure de-ionized (DI) water solution and the three nanofluids in the temperature range 30-80 °C are shown in Fig. 3. The result of ultrasonic velocity shows that the velocity in the nanofluids increases with the temperature and it becomes approximately constant after a certain temperature. Fig. 4 shows the frequency dependent ultrasonic attenuation in NiFe₂O₄ nanofluid. It illustrates that as the frequency increases the ultrasonic attenuation of nickel ferrite increases linearly throughout whole range of frequency.

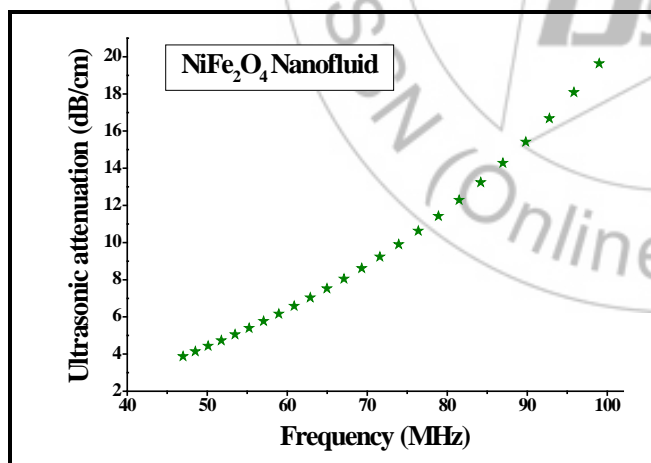


Figure 4: Frequency dependent ultrasonic attenuation in NiFe₂O₄ nanofluid

4. Conclusions

Nanofluids of NiO, Fe₂O₃ and NiFe₂O₄ have been successfully synthesized using sol-gel method. Particle size distribution of NiFe₂O₄ nanofluid determined by APS-100 have been found in the range 10-15 nm. Ultrasonic velocity measurements in the nanofluids have been studied using the ultrasonic interferometer at different thermal conditions.

5. Acknowledgment

Aashit Kumar Jaiswal acknowledges DST (Project no. SR/S2/CMP-0038/2011), New Delhi, India for financial support.

References

- [1] H. Nathani, R.D.K. Misra, Materials Science and Engineering B113 (2004) 228–235.
- [2] S. Singh, A. Singh, R.R. Yadav, P. Tandon, Materials Letters 131 (2014) 31-34.
- [3] T.J. Shinde, A.B. Gadkari, P.N. Vasambekar, Journal of Alloys and Compounds 513 (2012) 80– 85.
- [4] M.M. Rashad, O.A. Fouad, Materials Chemistry and Physics 94 (2005) 365–370.
- [5] S. Singhal, K. Chandra, Journal of Solid State Chemistry 180 (2007) 296–300.
- [6] P. Sivakumar, R. Ramesh, A. Ramanand, S. Ponnusamy, C. Muthamizhchelvan, Materials Research Bulletin 46 (2011) 2204–2207
- [7] A. More, V.M.S. Verenkar, S.C. Mojumdar, J. Therm. Anal. Calorim. 94 (1) (2008) 63–67.
- [8] P.S. Epstein, R.R. Carhart, J. Acoust. Soc. Am. 25 (1953) 553-565.